

DRYING SHRINKAGE OF HYDROTHERMALLY CURED CEMENTS WITH REACTIVE MAGNESIA AND CLAY BRICK WASTE

B. LIU¹, A. RAY² and P.S. THOMAS^{1,2*}

¹*Dept. Chemistry and Forensic Sciences, University of Technology Sydney PO Box 123, Broadway NSW 2007, Australia*

²*Centre for Built Infrastructure Research, University of Technology, Sydney, PO Box 123, Broadway NSW 2007, Australia*

**Email: paul.thomas@uts.edu.au*

ABSTRACT

In recent years, worldwide research and development in the cement industry has gathered momentum with an aim to explore innovative and sustainable methods to deliver environmentally responsible Portland Cement (PC) based construction products. This study investigated physical and mechanical properties of autoclaved cement-quartz sand blends with the addition of clay-brick waste (CB waste) and reactive magnesia (MgO) with the aim to lower CO₂ emissions through the reduction of PC consumption. Mechanical properties and drying shrinkage showed improvements with the incorporation of CB waste due to increased amounts and crystallinity of Al-tobermorite. The addition of reactive MgO to PC in hydrothermal conditions was observed to have a negative effect on the compressive strength. XRD data indicated that MgO did not take part in the reaction during the hydration of the cement and may even retard tobermorite formation. However, the expansive nature from the hydration of MgO to brucite may have compensated for drying shrinkage.

KEY WORDS

Portland cement; magnesia; clay brick waste; autoclave; drying shrinkage; compressive strength.

INTRODUCTION

While strength is an essential property of a building material, the durability characteristics are also regarded as being at least of equal if not of greater importance. It is crucial that a cement-based building material is capable of withstanding the conditions for which it has been designed throughout the life of a structure. Many causes for the lack of durability, categorised as physical, mechanical and chemical, can be attributed to external agents arising from the environment or by internal agents within the building material. One of the critical durability attributes of cement-based products is drying shrinkage. Drying shrinkage is the time dependent non-uniform dimensional change of a cement-based materials caused by the removal of water which can lead to cracking and warping (Juenger and Jennings, 2002). Even though drying shrinkage may not affect the structural integrity, the durability may be compromised over time (Bissonnette et al, 1999). Hydrothermal treatments are known to reduce drying shrinkage where tobermorite, the main binder in most autoclaved calcium silicate products, shrinks to about half the volume of the tobermorite gel (Kalousek, 1969). Shrinkage reduction is also afforded by the substitution of Al³⁺ in tobermorite under autoclaving. Noorlander (1964) found that with increasing kaolin or gibbsite additions to the raw mix, the drying shrinkage of autoclaved sand-lime bricks decreased progressively. Sun et al. (1983) quantified hydrates in numerous autoclaved aerated concrete (AAC) specimens and reported that the proportion of different

hydrates including tobermorite, C-S-H and hydrogarnet was important to achieve a compromise between strength and drying shrinkage. Drying shrinkage was found as a function of the C-S-H content where the greater the amount of C-S-H, the greater was the drying shrinkage.

This study investigated drying shrinkage properties of autoclaved blends incorporating fired clay-brick (CB) waste fines and reactive magnesia (MgO). CB waste, an abundant industrial waste, is a supplementary cementing material (SCM) rich in alumina and silica and has been shown to exhibit pozzolanic activity under ambient conditions when finely ground (Wild et al, 1998). Reactive or light-burned MgO (produced at calcination temperatures of 600°C to 900°C) has been recognised as a potential additive to produce blended cement where its production, relative to PC, is less energy intensive. It had been suggested in previous studies (Buntoro, 2000, Taylor, 1997, Xu and Deng, 2005) that reactive MgO is utilised as an expansive additive to produce a shrinkage-compensated cement. The hydration of MgO to brucite ($\text{Mg}(\text{OH})_2$), which involves a volume expansion of 118% (Rehsi and Majumdar, 1969), may fill in pore spaces when water is evaporated to reduce capillary stress and prevent the pores from collapsing. This paper aims to further studies previously carried out by the authors (Liu et al, 2007) in the subject of strength development and phase characterisation. The Al_2O_3 present in CB waste provided a source of Al ions for the formation of Al-substituted tobermorite and, in conjunction with enhanced formation of C-S-Hs, resulted in strength improvement of approximately 9% for up to 15% addition. The addition of MgO alone resulted in a relative reduction in the proportion of PC available for the formation of hydration products and a reduction in compressive strength of approximately 16% at 20% addition was observed. The addition of MgO had also adversely affected the formation of Al-tobermorite. The combined additions of MgO and CB waste, however, produced a strength gain equivalent to the CB waste only series up to 15% with partial retainment of 5% strength gain at 20% addition. The authors suggested that the volume expansion of MgO to brucite and, to a lesser extent, its subsequent carbonation to MgCO_3 had a complementary physical effect in that it behaved as an expanding filler producing more efficient packing leading to retainment of strength as crystallisation of the Al-tobermorite occurred.

EXPERIMENTAL

Raw Materials

Raw materials used in this study were sourced from local suppliers. These are listed as follows with the oxide compositions listed in Table 1.

- a) Goliath cement (OPC) was supplied by Australian Cement, Auburn, NSW, Australia. The material has a fineness index (Blaine) of $350\text{m}^2/\text{kg}$.
- b) Type 200G ground silica (quartz sand) was supplied by Unimin Australia Limited, Sydney, Australia, with a Blaine value of $360\text{m}^2/\text{kg}$.
- c) Natural magnesite (MgCO_3), with surface area of $2.3\text{m}^2/\text{g}$, was supplied by Unimin Australia Limited, Sydney, Australia. It has a bulk density of 1.6 g/cm^3 and a particle size range of less than $75\mu\text{m}$ with a maximum of 2% greater than $75\mu\text{m}$. The magnesite was calcined to light-burned magnesia at 600°C for 2 hours. BET surface area of calcined MgO was measured to be $104.2\text{m}^2/\text{g}$.
- d) Clay-brick (CB) waste used was from a major clay-brick manufacturer in Sydney, Australia. The pre-screened brick waste was ground by dry ball milling method to produce a surface area comparable to that of the quartz sand. Crystalline phase identification of the CB waste was determined using XRD and these phases are listed in decreasing order of abundance as follows: quartz (SiO_2); mullite ($3\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2$); Hematite (Fe_2O_3); cristobalite (SiO_2); rutile (TiO_2).

Table 1. Chemical compositions of the raw materials used in this investigation

Oxides	OPC	Silica	Magnesite	Brick waste
SiO ₂	20.0	98.9	6.15	69.71
Al ₂ O ₃	4.5	0.6	1.60	18.64
Fe ₂ O ₃	3.7	0.1	0.60	7.48
CaO	64.2	0.1	1.16	0.21
MgO	1.48	0	44.11*	0.95
K ₂ O	0.67	-	0.28	1.88
Na ₂ O	0.052	-	0.42	0.44
TiO ₂	0.27	0.06	0.086	0.84
LOI	3.1	0.1	46.47	0.08

Oxides and LOI are in mass %.

*Magnesium Carbonate equivalent = 92.3%

Chemical compositions of OPC and 200G silica were obtained from the suppliers. Chemical compositions of magnesite and brick waste were determined by X-ray Fluorescence (XRF) spectroscopy.

Mix design

Three series of OPC mixtures were prepared using a water-to-total solid mass ratio (w/s) of 0.35 and with a constant total Ca/Si oxide molar atom ratio of 0.49 (i.e. atomic ratio based on a 45:55 cement to quartz % mass ratio). The first series of mixtures is concerned with the addition of MgO (M series) at 0, 5, 10 and 20 mass % and the second series with the addition of CB waste (C series) at 0, 10 and 20 mass %. The third series deals with the addition of both MgO and CB waste (CM series) in equal amounts having the total combined amount of 0, 5, 10, 15, and 20 mass %.

Testing and Analysis

Mechanical mixing was conducted on the mixes in accordance with ASTM C 305-99 (1999) using a Hobart mixer. Pastes were cast into stainless steel moulds and compacted on a vibratory table, followed by a 24 hours curing period in a moist cabinet (temperature $23 \pm 1^\circ\text{C}$, 95% relative humidity as per ASTM 511-03 (2003)). Demoulded specimens were autoclaved for 7.5 hours, 6 hours of which were at 180°C under approximately 1 MPa of pressure in saturated steam. Drying shrinkage was measured on three autoclaved prisms per selected mix as per ASTM C 490-04 (2004). Dimensions of the prisms used were $120 \times 16 \times 16$ mm instead of $285 \times 25 \times 25$ mm as suggested by the ASTM method. Specimens were fully saturated in water for 3 days followed by equilibration to a relative humidity (RH) of approximately 50-55% by placing the prisms on racks over a saturated solution of $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ as per ASTM E104-85 (1996) in a closed plastic box. Relative humidity and temperature were continuously recorded using a HOBO[®] RH/Temp data logger. A special jig mounted at an angle of 45° was used to measure the prisms. Length measurements, using a Mitutoyo Digimatic caliper recorded to the nearest 0.001 mm, were carried out every 2-4 days until the shrinkage remained constant (approximately 4 weeks).

XRD analyses were performed using a Siemens D5000 diffractometer operating at 40 kV and 30 mA with CuK_α radiation scanning from 3 to $60^\circ 2\theta$ at intervals 0.02° using a step time of 8 seconds per interval. Peak intensity and integrated areas were determined by Scherrer method using TOPAS 2.0 with correction for line broadening using a fundamental parameters approach for X-ray line profile fitting (Cheary, R.W. and A. Coelho, 1992). The crystallinity of the tobermorite phase was determined using the relative intensities of the 002 and 220 reflections Hara, N. and H.G. Midgley, 1980), i.e. ($H_{0.308}/H_{1.1}$).

RESULTS AND DISCUSSION

Figure 1 depicts a general reduction in drying shrinkage of autoclaved blends with increasing addition of CB waste fines in both C and CM series. The observed improvement in drying shrinkage can be explained by the main hydration products formed where the presence of Al in CB waste accelerated the crystallisation of Al-bearing 1.1 nm tobermorite from C-S-H. Al-tobermorite has been shown to be relatively more resistant to drying shrinkage (Noorlander, 1964) whilst reduced proportion of C-S-H, which is highly porous, will additionally improve the dimensional stability (Juenger and Jennings, 2002).

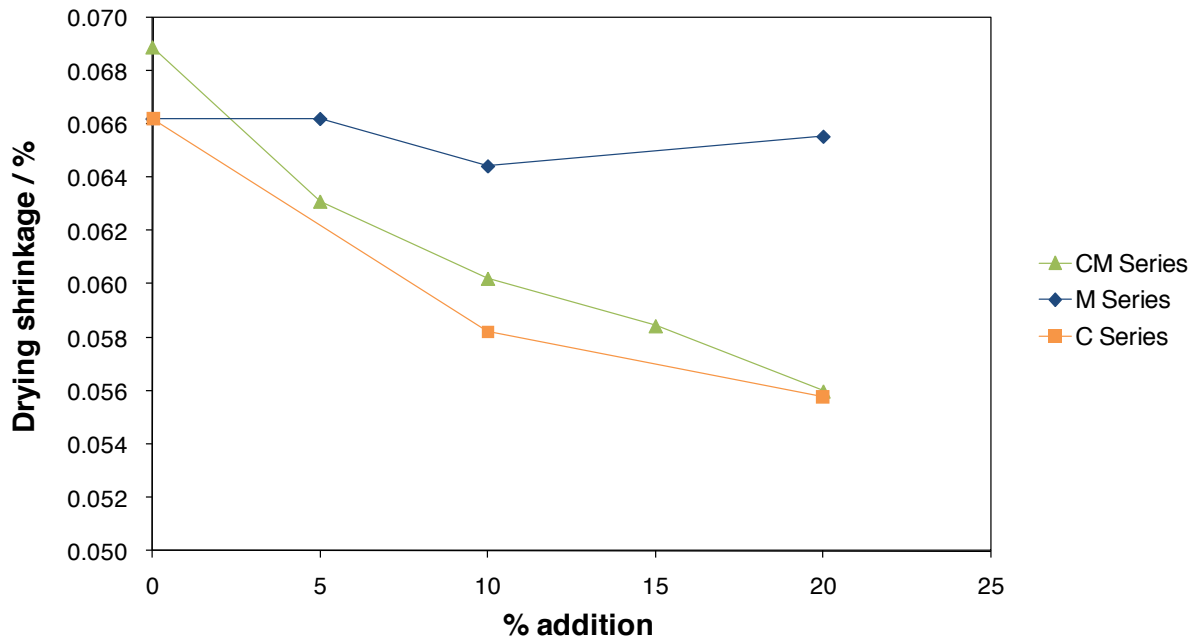


Figure 1 – Average drying shrinkage of selected specimens after approximately 28 days.

The most notable feature is the equivalent degree of drying shrinkage reduction afforded in the C20 and CM20 (10% CB waste, 10% MgO) specimens, despite the fact that the amount of Al-tobermorite is significantly greater in the C20 specimens (Liu et al, 2007). Furthermore, the CM20 specimens exhibited superior drying shrinkage performance when compared to the corresponding CB waste content specimens (C10 specimens). The addition of reactive MgO in the CM20 specimens may have resulted in the high degree of reduction in shrinkage at half the amount of CB waste addition. The volume increase associated with the hydration of magnesia to brucite and subsequent carbonation to magnesite may compensate for the increase in shrinkage from the reduction in the amount and crystallinity (Figure 2) of Al-tobermorite. This may also explain the relatively constant shrinkage values observed for the M series specimens while the tobermorite quantity and crystallinity progressively decreased with increasing MgO additions as the proportion of PC available for the formation of hydration products is reduced. This is evident in Figure 2 where the M series specimens deviated from the main linear trend exhibited by the C series and CM series specimens.

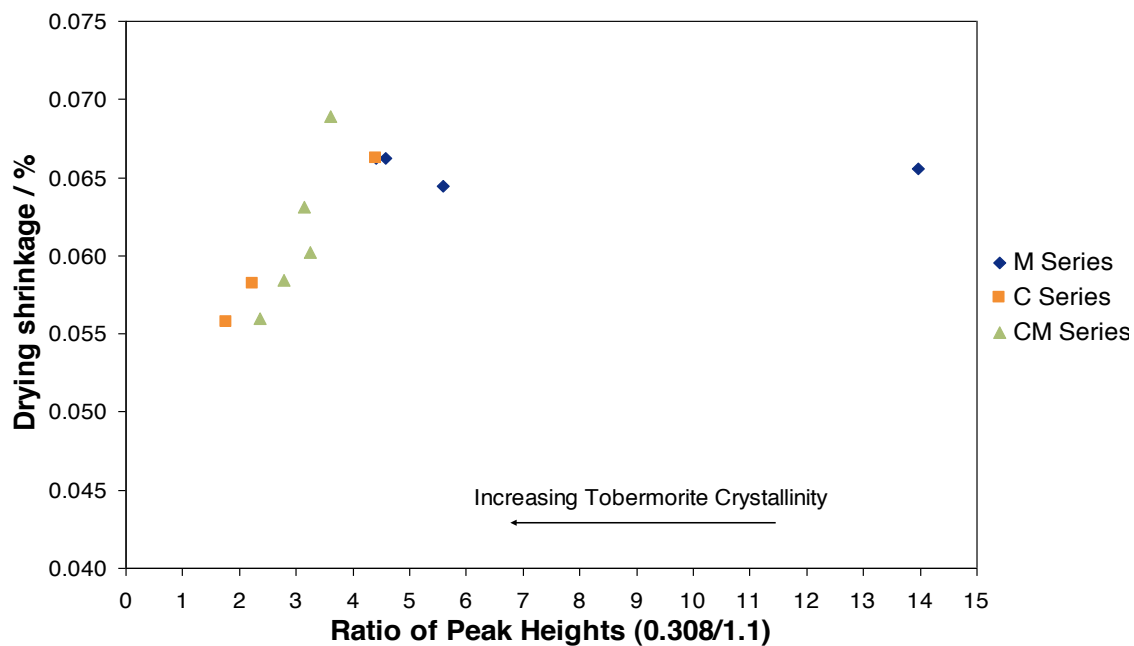


Figure 2 – Drying shrinkage versus the degree of crystallinity of tobermorite calculated from ratio of peak heights of the 0.308 nm and 1.1 nm XRD peaks.

CONCLUSIONS

The proportion and crystallinity of tobermorite was found to have a decisive influence on drying shrinkage where minimum shrinkage was associated with the addition of CB waste leading to the formation of highly crystalline Al-tobermorite from C-S-H. The addition of reactive MgO yielded relatively constant shrinkage values which were attributed to the expansive nature of magnesia converting to brucite and subsequent carbonation to magnesite. The combined CB waste and MgO series produced comparable shrinkage values in comparison to the CB waste added only specimens, which was afforded by complementing physical packing and phase developments.

REFERENCES

- ASTM E104-85. 1996. "Standard Practice for Maintaining Constant Relative Humidity by Means of Aqueous Solutions". ASTM International: Philadelphia.
- ASTM C305-99. 1999. "Standard practice for mechanical mixing of hydraulic cement pastes and mortars of plastic consistency". ASTM International: Philadelphia.
- ASTM C511-03. 2003. "Standard practice for mixing rooms, moist cabinets, moist rooms, and water storage tanks used in testing of hydraulic cements and concretes". ASTM International: Philadelphia.
- ASTM C305-99. 2004. "Standard practice for use of apparatus for the determination of length change of hardened cement paste, mortar, and concrete". ASTM International: Philadelphia.
- Bissonnette, B., Pierre P., and Pigeon M. 1999 "Influence of key parameters on drying shrinkage of cementitious materials". *Cement and Concrete Research*, 29(10), 1655-1662.
- Buntoro, A. 2000. "The effect of neat magnesium oxide (MgO) as expanding additive on cement shear bond strength at high temperature up to 2500C". in *Proceedings World Geothermal Congress 2000*. Kyushu-tohoku, Japan.

- Cheary, R.W. and Coelho A. 1992 "A fundamental parameters approach to x-ray line-profile fitting. *Journal of Applied Crystallography*". 25(2), 109.
- Hara, N. and Midgley H.G. 1980. "The determination of crystallinity of tobermorite in autoclaved products". *Cement and Concrete Research*, 10(2), 213-221.
- Juenger, M.C.G. and Jennings H.M. 2002. "Examining the relationship between the microstructure of calcium silicate hydrate and drying shrinkage of cement pastes". *Cement and Concrete Research*, 32(2), 289-296.
- Kalousek, G.L. 1969. "High temperature steam curing of concrete at high pressure". in *5th International Symposium of the Chemistry of Cement*.: Tokyo. 523-537.
- Liu, B., Ray A., and Thomas P. 2007 "Strength development in autoclaved aluminosilicate rich industrial waste-cement systems containing reactive magnesia". *Journal of the Australian Ceramic Society*. 43(1), 82-87.
- Noorlander, A. 1964. "Reducing shrinkage of calcium silicate bricks. in *Proceedings of the International Symposium on Autoclaved Calcium Silicate Building Products*". London.
- Rehsi, S.S. and Majumdar A.J. 1969. "High-magnesia portland cements: studies on cements prepared with reagent-grade chemicals". *Magazine of Concrete Research*. 21(67), 67-78.
- Sun, G.K., Li G., and Jia C. 1983. "Relation between hydrates and the strength and shrinkage of autoclaved aerated concrete". *Chemical Abstracts*. 99, 42560-42556.
- Taylor, H.F.W. 1997. "Cement Chemistry". 2nd ed., London: Thomas Telford.
- Wild, S., Gailius A., hansen H., Pederson L., and Szwabowski J. 1998. "COPERNICUS RESEARCH PROJECT: Recycling of Waste Clay Brick and Tile Material for the Partial Replacement of Cement in Concrete". 1995-1998, European Commission, Brussels.
- Xu, L. and Deng M. 2005. "Dolomite used as raw material to produce MgO-based expansive agent". *Cement and Concrete Research*,. 35(8), 1480-1485.

CONTENTS

Guest Speaker

Bentur, A.

Aging mechanisms and durability performance of inorganic bonded fiber composites 10

Session 1 · Supplementary Cementitious Materials - Part I

Moesgaard, M

Optimal composition of calcium aluminosilicate glass particles used as supplementary cementitious materials 22

Stenberg, M.

Mechanical performances of blended portland cements containing glass particles and fibers 30

Thomas, P.

Pitchstone Fines: A new development in Portland cement-based construction products 39

Ganjian, E.

Effect of lime stone powder on mechanical property of cement composite board 48

Session 2 · Supplementary Cementitious Materials - Part II

Lin, Z.:

The effect of microsilica on carbonation of air-cured fiber cement 60

Barbosa de Souza, R.

The influence of silica fume on the mechanical strength and drying shrinkage of fiber cement reinforced with PVA fiber 80

Thomas, P.

Drying shrinkage of hydrothermally cured cements with reactive magnesia and clay brick waste 90

Session 3 · Fiber Properties and Reinforcement - Part I

Fuente, E.

Use of wastes as raw materials in fiber reinforced cement manufacture 98

Tonoli, G. H. D.

Effects of eucalyptus fiber surface properties on the microstructure of cement based composites 105

Session 4 · Fiber Properties and Reinforcement - Part II

Krnel, K.

The fracture strength of fiber cement corrugated sheets: a statistical approach using Weibull analysis 116

Passé-Coutrin, N.M.

Bagasse reinforced cement composites: Effect of fiber treatment 130

Olorunnisola, A. O.

Influences of particle size and cement content on properties of cement-bonded composites from eucalyptus veneer waste 140

Gross, G.

Bi-component and mono-component polypropylene fibers used in fiber cement for reinforcement 149

Session 5 · Production Process

Cooke, T.

Selection and performance of flocculents for Hatschek made air cured fiber cement 158

Tihlarik, P.

Possibilities of fiber cement extrusion 180

Ingelsberger, E.

New testing equipment for short fibers 189

Session 6 · Production Plant

Quang, D. Q.

Hatschek machine and equipment for non-asbestos fiber reinforced cement sheets 202

Ang, S. H.

Cutting technology of autoclaved cellulose fiber reinforced cement board 213

Dietz, T.

New concepts for fiber cement production plants 223

Session 7 · New Product Properties

Cechmanek, R.

Influence of carbon admixtures on electrical properties of inorganic fiber cement composites 236

Lecomte, J.-P.

Hydrophobic protection of fiber reinforced cement boards with silicon-based materials 246

Session 8 · New Applications

Van Elten, E. J.

New developments in the field of wood cement products, applications and production technologies 260

Ajayi, B.

Public-Private Partnership in housing delivery using cement-bonded composites building materials 271

Yamada, K.

Application of DFRCC thin board to passive-vibration-control panel for wooden frame 281

Brasca, M.

Innovative fibre-cement solutions for smart-eco buildings of 2020-30 289

Posters

Čechmánek, R.

Effect of dispersive non-metallic fibre reinforcement on fine-grained cement composite properties 302

Koplík, J.

Stabilization of fly-ash containing heavy metals by alkali activation 311

Buzek, L.

Aluminosilicate system based on alkali activation of industrial by-products reinforced with wollastonite microfibers 316

Másilko, J.

Improving the water resistance of macro-defect-free cement 321


Ghussn, L.

Coated fiberglass for cement based composites 326


Exhibitors Large



Exhibitors Standard

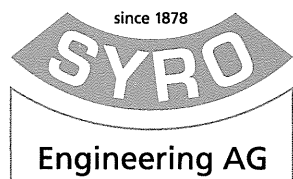

Sponsors Standard



AC CUBED CONSULTING
MANY DIMENSIONS OF EXPERIENCE IN
CEMENT & CONCRETE TECHNOLOGY



Moslemi Excellence Award



IIBCC 2010

International Inorganic-Bonded Fiber Composites Conference

PROCEEDINGS

21 - 24 September 2010
Aalborg, Denmark

Edited by:
Eigil V. Sorensen, Aalborg University
Henning M. Thygesen, Cembrit

12TH INTERNATIONAL INORGANIC-BONDED FIBER COMPOSITES CONFERENCE



Proceedings of the 12th International Inorganic-Bonded Fiber Composites Conference

Edited by: *Eigil V. Sorensen, Aalborg University*

Henning M. Thygesen, Cembrit

Printed by: *vahle+nikolaisen – 250 copies*

Published by: *Aalborg University,*

Department of Civil Engineering

57 Sohngaardsholmsvej, 9000 Aalborg,

Denmark

www.civil.aau.dk

civil@civil.aau.dk

Phone: +45 9940 9940

September 2010

ISBN 87-91606-20-9

PREFACE

Every two years the IIBCC (International Inorganic-Bonded Fiber Composites Conference) provides the perfect opportunity for technical interaction between people with a common interest in all types of inorganic-bonded fiber composite materials and products including fiber-cement, fiber-gypsum, fiber-ceramics, wood cement products (WWCB, CBPB, WRCB), brick and block composites. A wide variety of these technologies form the basis of extensive manufacture around the world while others are still in the concept stage.

Manufacturers, potential customers, key suppliers and experts from around the world meet at this conference to learn about the latest scientific and technological advances within this area as well as to expand their knowledge of the market perspectives while networking and developing business relationships.

We have the honor of hosting the 12th conference in this series – the IIBCC 2010 - in Aalborg, Denmark. A large number of very interesting papers and posters have been submitted to the IIBCC 2010 by leading experts, presenting recent developments and findings relevant to inorganic-bonded fiber composites technology and production. These papers and posters are published in the present proceedings, organized by subject area. During the conference the Moslemi Excellence Award will be presented to the most outstanding research or development contribution advancing the sustainability of fiber cement. The award-winning paper will be published as an addendum to the proceedings.

We are positive that the presentations and discussions at the conference will provide important new knowledge and information to the benefit of inorganic-bonded fiber composite materials, manufacture, and products. We wish you a good IIBCC 2010.

Eigil V. Sorensen
Henning M. Thygesen

REVIEW OF PAPERS

Each paper in the present proceedings has been reviewed by two expert referees prior to being published and presented at the IIBCC 2010 conference. The Organizing Committee gratefully acknowledges the effort provided in this important task by the following persons:

Stephen Akers, Switzerland

Tony Cooke, Australia

Silvia Delvasto, Colombia

Luc Van der Heyden, Belgium

Vanderley M. John, Brazil

Andrew Kupferschmid, Switzerland

Benoit de aLhoneux, Belgium

Carlos Negro, Spain

Lin Zhen, China

Holmer Savastano Jr., Brazil

Eigil V. Sorensen, Denmark

Henning M. Thygesen, Denmark

IIBCC 2010

PROCEEDINGS

12th International Inorganic-Bonded Fiber Composites Conference

Speakers and Papers

Sponsors/exhibitors

Learn more about Aalborg

Aalborg · Denmark
21 - 24 September 2010

www.iibcc.net